

THE ROLE OF PHOSPHORUS AND SULFUR IN INCONEL 718 *

Xishan Xie, Xingbo Liu, Yaohe Hu, Bin Tang, Zhichao Xu, Jianxin Dong and Kequan Ni
University of Science & Technology Beijing, Beijing 100083, China

Yaoxiao Zhu
Institute of Metal Research, Academy of Sciences, Shenyang 110015, China

Shusen Tien
Fushun Steel Plant, Fushun 113001, China

Laiping Zhang
No.3 Steel Works of Changcheng Special Steel Co., Sichuan 621704, China

Wei Xie
Shanghai No.5 Steel Works, Shanghai 200940, China

Abstract

Phosphorus and sulfur are generally regarded as the most common impurities and detrimental elements in nickel-base superalloys. For further understanding the role of P and S in Inconel 718 nine experimental heats were melted on the base of conventional Inconel 718 chemical composition with variation of P (from 10 to 130 ppm) and S (from 15 to 175 ppm) respectively. Phosphorus and sulfur both have almost no influence on strengths and ductilities at room temperature tensile test. Phosphorus also has no effect on the yield and ultimate strengths and elongation at 650°C tensile test. However, sulfur has an obviously decreasing effect on 650°C tensile elongation but no effect on yield and ultimate strengths.

Sulfur has a remarkable detrimental effect on stress rupture life and especially on ductility loss at 650°C. However, phosphorus is in total difference to sulfur effect, generally can increase stress rupture life and ductility both.

Microstructure observation on grain structure, δ -phase and strengthening phase γ'' and γ' can not reveal the effect of P and S on the morphology and amount of precipitates. Fractography analyses show different patterns of stress rupture specimens with the variation of P and S contents. Experimental results lead us to consider the segregation behaviors of P and S at grain boundaries, however the effect of P and S should be different.

Background and Industrial Tests

The clean superalloy production is regarded to meet the strict demand of aero-engine and gas-turbine industries and cleanliness has been basically considered in two categories, i.e. inclusions and detrimental elements control⁽¹⁾. Phosphorus and sulfur are generally regarded as the most common impurities and detrimental elements in Ni-base superalloys. From the points of view on melting process improvement at industrial alloy production background and on basic understanding the role of P and S in Ni-base superalloys the present investigation was conducted in industrial and laboratorial scales.

Niobium segregation and Laves phase formation during solidification from molten metal has been regarded as the most serious problem in Inconel 718 production. Results of segregation study during solidification by means of metalography and electron-probe analyses show that P and S most seriously aggravate dendritic segregation by decreasing solidus temperature and lowering the maximum content of Nb in γ solid solution and also moving the eutectic point ($\gamma + \text{Laves}$) to the higher content of Nb in the pseudo-binary phase diagram⁽²⁾. In result of these effects P and S (especially P) will favour the formation of isolated large-size blocky Laves phase instead of eutectic Laves^(2,3). Based on above mentioned experimental results the low segregation Inconel 718 with very low content of P ($P < 10 \text{ ppm}$) VIM+VAR industrial ingots (with diameters 406 or 423mm) were melted in Chinese steel works^(2,4).

The comparison of solidified structure sliced directly from the industrial production ingots (low segregation and conventional) shows the advantage of lower segregation and less amount of blocky Laves phase especially at the mid-radius and the center of low segregation Inconel 718

* This project is supported by the Chinese National Natural Science Foundation and the Ministry of Metallurgical Industry.

Table I. Example of the Mechanical Properties Comparison between Low Segregation and Conventional Inconel 718 Die-Forging Disks.

Alloy	20°C				650°C				650°C, 686MPa	
	YS	UTS	EL	RA	YS	UTS	EL	RA	T	EL
	(MPa)	(MPa)	(%)	(%)	(MPa)	(MPa)	(%)	(%)	(hrs)	(%)
L. S.	1068	1268	25.0	37.5	1060	1197	14.8	27.0	55	14.4
Con.	1038	1289	20.8	34.5	1005	1172	21.2	33.3	47	22.8

* L.S.-- low segregation In 718; Con.-- conventional In 718.

ingots with very low contents of phosphorus (<10ppm). High temperature homogenization heat treatment tests show the easier tendency to reach homogenized structure, i.e. to eliminate Nb segregation to the lowest degree. However, Nb segregation of both ingots (low segregation and conventional) can be eliminated to meet industrial demand after 2 step high temperature long time homogenization treatment (first step for Laves phase solution and the second step for homogenization of Nb).

Mechanical property test results including room temperature tensile, 650°C tensile and stress rupture, stress controlled LCF, stress controlled fatigue and creep interaction properties determination at 650°C for die-forging disks(~500mm diameter) have not revealed advantages of low segregation Inconel 718 in comparison with conventional Inconel 718 as shown in Table I and Figure. 1.

For further understanding the role of P in comparison with the role of S in Inconel 718, nine experimental heats were melted on the base of conventional Inconel 718 composition with the variation of P (from 10 to 130ppm) and S (from 15 to 175ppm) respectively.

Materials and Experimental Procedure

Nine experimental heats of Inconel 718 with variation of P and S were melted in 25kg VIM furnace and poured in 15kg ingots. Chemical composition and alloy designation are shown in Table II.

Nine ingots were conducted with 2 step homogenization treatment i.e., 1160°C/24hrs → 1180°C/24hrs/A.C. All the ingots were forged down to 40mm square bars and finally hot rolled to 18mm round bars for tensile tests at room temperature and 650°C, stress rupture and creep tests were conducted at 650°C, 686MPa and 725MPa respectively. Structural characterization and fractography analyses were carried out by means of optical, SEM and TEM microscopy.

Results and Discussion

The content of P and S in the range less than 130 ppm and 175 ppm respectively, both elements have almost no effect on tensile strengths (UTS and YS) and ductility (EL) at room temperature (see Fig.2 and 3). Phosphorus also has no effect on the strengths and ductility at 650°C tensile test (see Fig.2b). However, sulfur has an obviously decreasing effect on 650°C tensile elongation as indicated in Fig.3b.

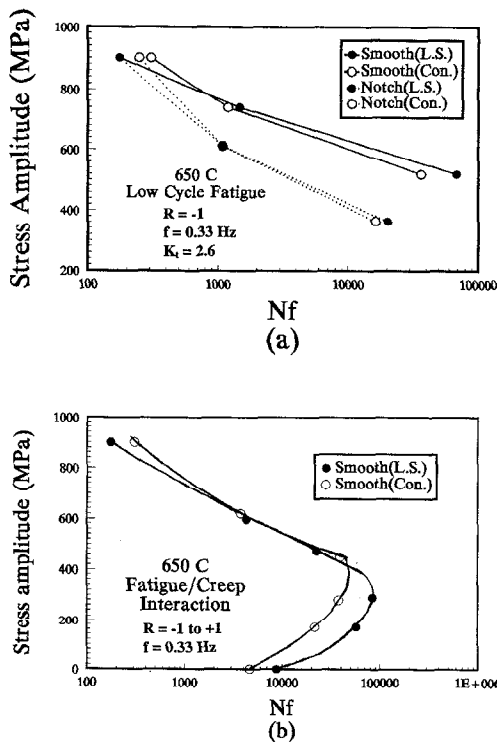


Figure 1 Stress controlled LCF(a) and fatigue/creep interaction(b) properties of low segregation and conventional IN718 disks.

Table II. Chemical Composition of Test Alloys (wt%)

Alloy	C	Mn	Si	S	P	Ni	Cr	Mo	Al	Ti	Nb	B	Fe
P1	0.02	0.02	0.05	.001	.0010	52.52	18.69	3.01	0.52	1.01	5.20	.005	bal.
P2	0.03	0.02	0.05	.002	.0025	52.38	18.62	2.98	0.47	1.01	5.15	.005	bal.
P3	0.03	0.02	0.06	.003	.0033	52.79	18.56	3.01	0.52	1.00	5.24	.006	bal.
P4	0.02	0.02	0.05	.003	.0083	52.76	18.45	3.05	0.52	1.01	5.17	.006	bal.
P5	0.02	0.02	0.05	.003	.0130	52.90	18.76	3.01	0.50	1.01	5.17	.005	bal.
S1	0.04	0.02	0.05	.0015	.004	52.52	18.52	2.98	0.54	1.02	5.18	.005	bal.
S2	0.04	0.02	0.11	.0050	.004	52.70	18.56	2.95	0.49	1.01	5.22	.005	bal.
S3	0.02	0.02	0.06	.0145	.001	52.44	18.52	2.95	0.54	1.05	5.15	.005	bal.
S4	0.02	0.02	0.06	.0175	.001	52.64	18.45	2.97	0.55	1.01	5.11	.005	bal.

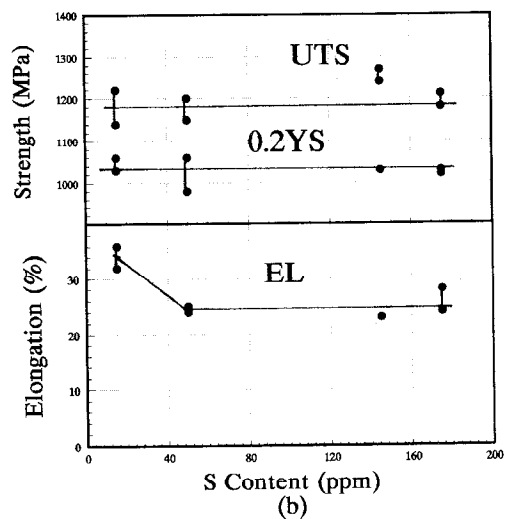
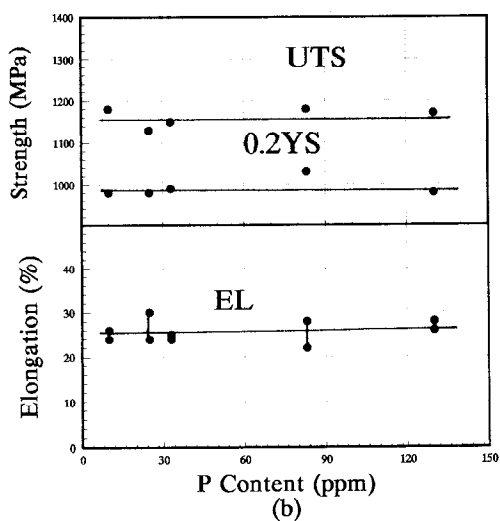
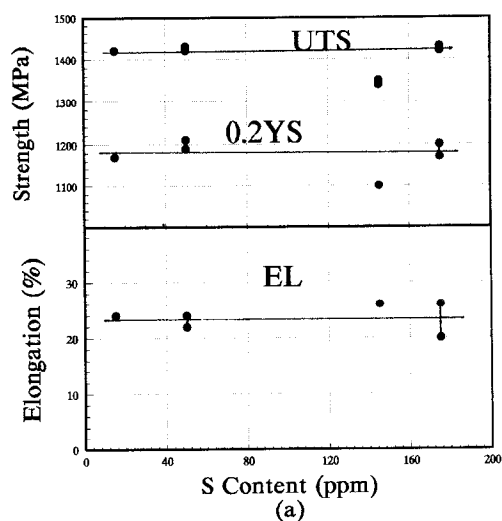
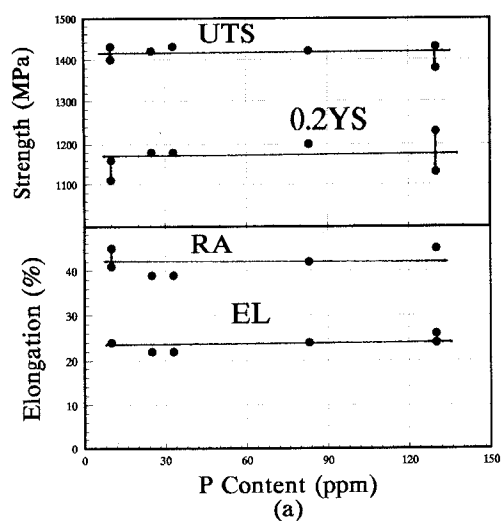


Figure 2 Effect of phosphorus on tensile properties at room temperature (a) and 650°C (b) of IN718.

Figure 3 Effect of sulfur on tensile properties at room temperature (a) and 650°C (b) of IN718.

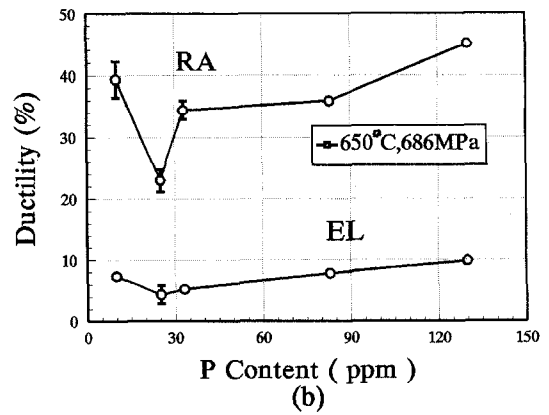
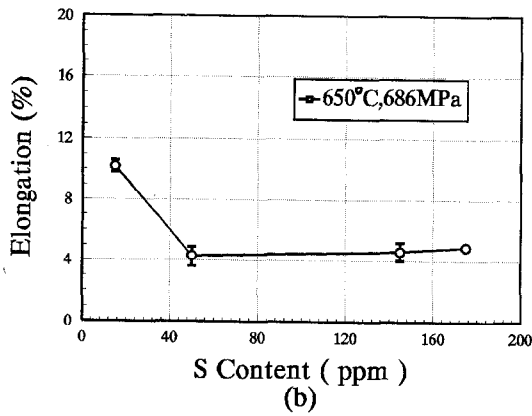
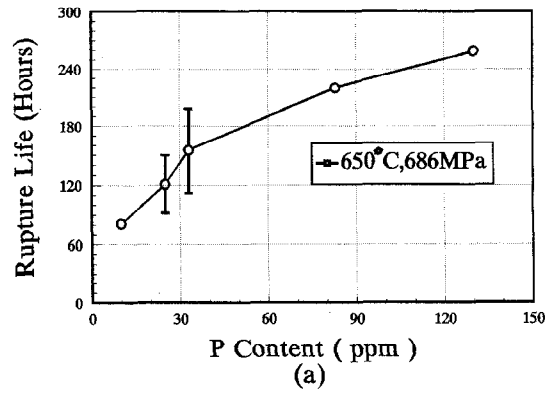
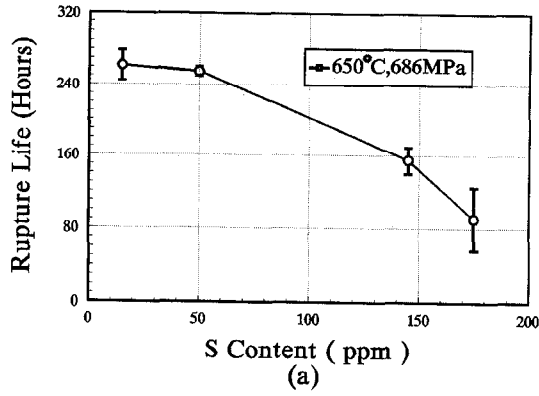


Figure 4 Effect of sulfur on 650°C, 686MPa stress rupture life (a) and ductility (b) of IN718.

Figure 5 Effect of phosphorus on 650°C, 686MPa stress rupture life (a) and ductility (b) of IN718.

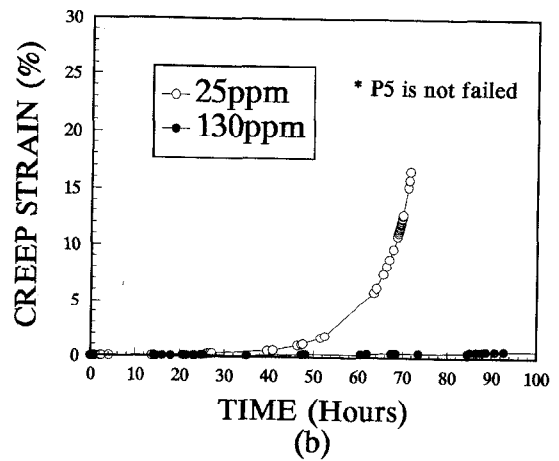
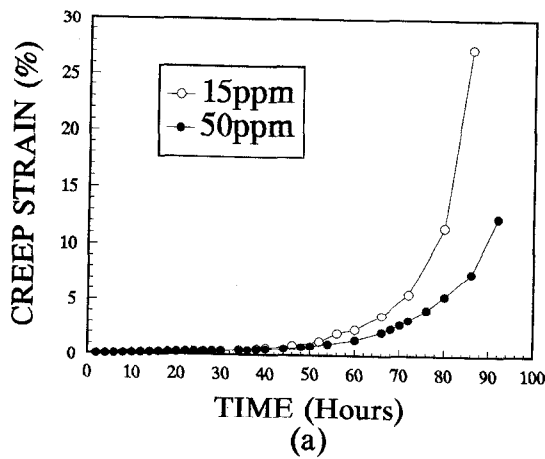


Figure 6 Effect of sulfur (a) and phosphorus (b) on 650°C, 725MPa creep curves of IN718.

Sulfur has a remarkable detrimental effect on stress rupture life and especially ductility loss even at a small amount of sulfur content in Inconel 718 as shown in Fig.4. However, phosphorus is in total difference to sulfur effect, P can increase stress rupture life and ductilities (see Fig.5). It implies that P has certain strengthening and ductility improvement effects. Special attention should be paid, that Alloy 718 with low content of P (~20ppm) is susceptible to the lowest ductilities at 650°C stress rupture test (Fig.5b shows the “lowest valley” of stress rupture ductility curve), which shows consistency with the experimental results of Cao and Kennedy⁽⁵⁾.

Creep test results at 650°C show that S and P have no influence on secondary creep rates, However, phosphorus can prolong secondary creep stage tremendously (Fig.6b). In results of that Alloy 718 with higher content of phosphorus characterizes with longer creep failure life.

Microstructure observation on grain structure, δ -phase at grain boundaries, γ'' and γ' precipitates in the grains can not reveal the effect of P and S on the grain size and morphology and amount of precipitates (see Fig.7 and 8).

Metallographic observation on the longitudinal sections of stress rupture failure specimens shows typical grain boundary cracks in all specimens with different contents of S and P respectively. These results show all the failures at 650°C stress rupture tests characterize with intergranular fracture. Alloy 718 with low content of S (Alloy S1 with 15ppm sulfur) clearly shows deformed and prolonged grain structure (see Fig.9a) because of the longer stress rupture life and higher ductility of Alloy S1 in comparison with Alloy S4 (175ppm sulfur) as shown in Fig.9b. However, Alloy P5 with highest content of P(130ppm)



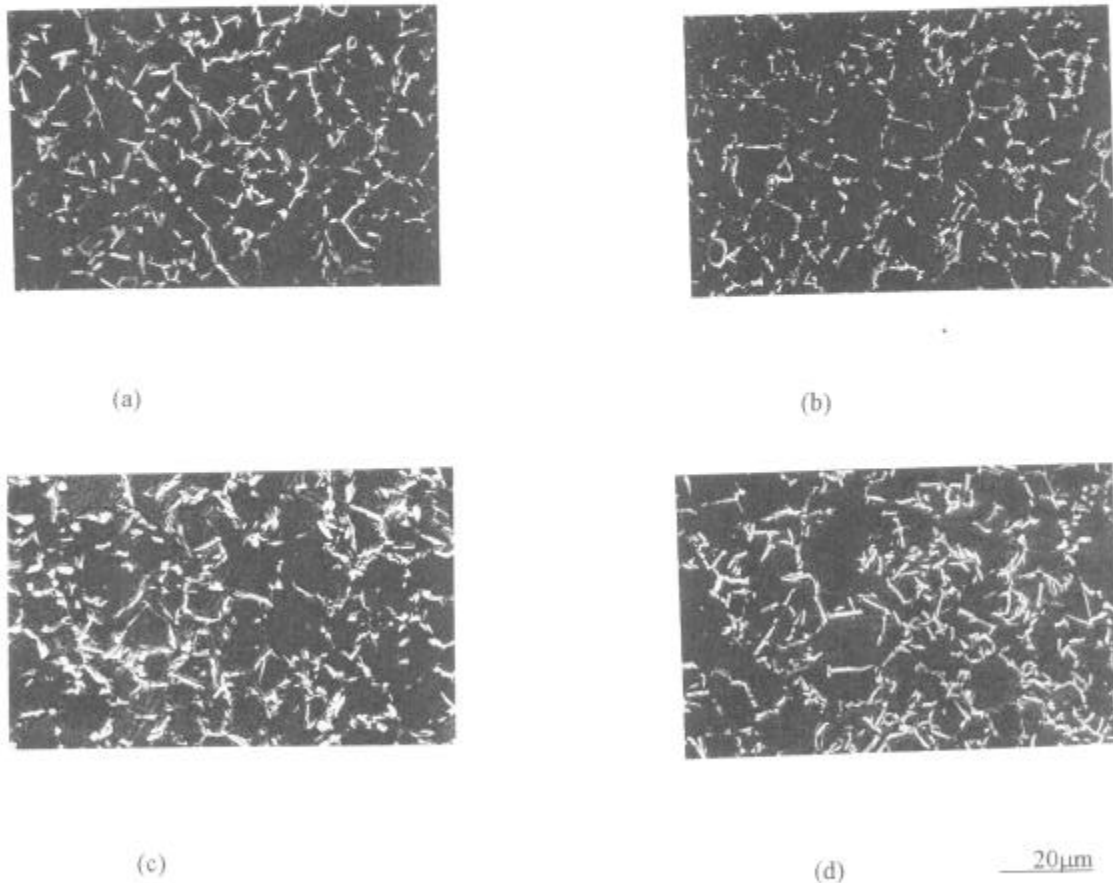


Figure 7 Effect of sulfur and phosphorus on grain structure and δ -phase in IN718.
a - S1(15ppm S); b - S4(175ppm S); c - P2(25ppm P); d - P5(130ppm P)

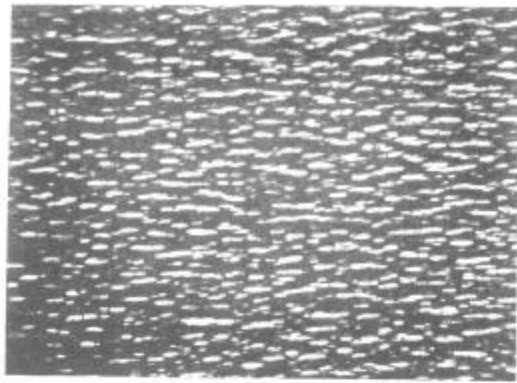


(a)

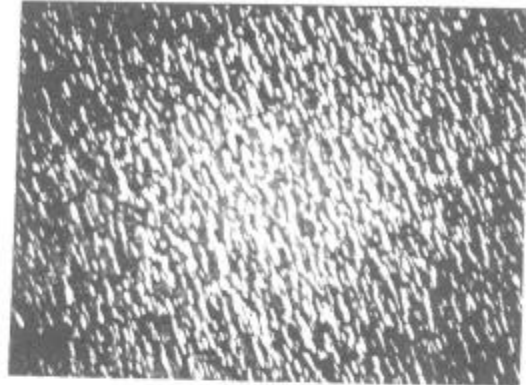


(b)

200nm


Figure 8 Effect of sulfur and phosphorus on γ'' and γ' precipitates in IN718.
a - P5(130ppm P, 30ppm S); b - S4(10 ppm P, 175 ppm S).

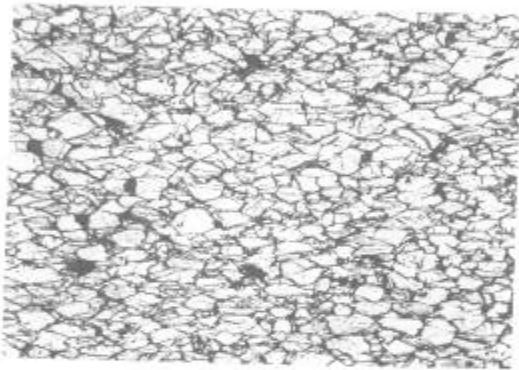


(a)

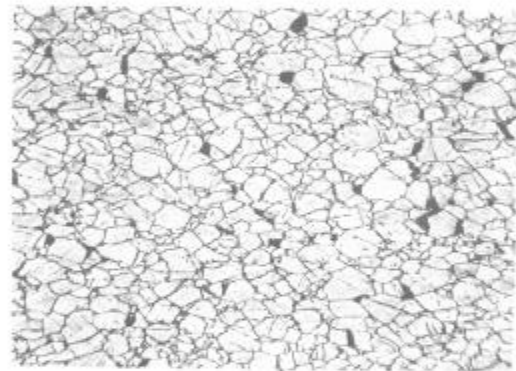

(b)

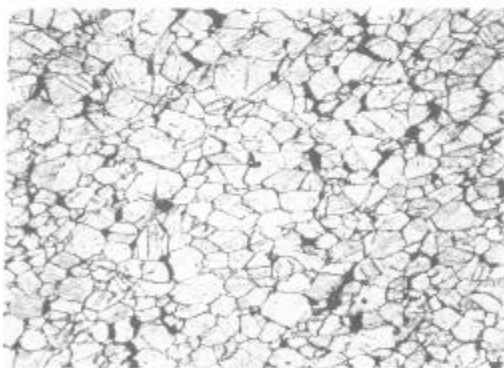

(c)

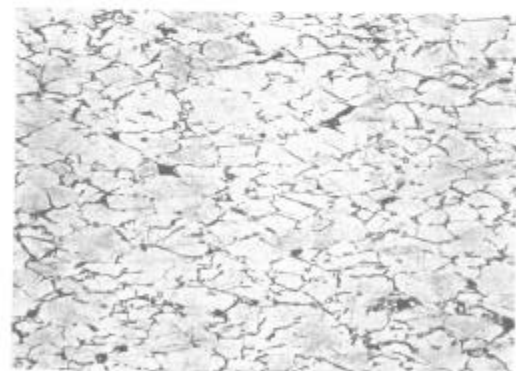

(d)

50μm

Figure 9 Effect of sulfur and phosphorus on fracture manner at longitudinal direction of 650°C stress rupture failed specimens.

a - S1(15ppm S); b - S4(175ppm S); c - P2(25ppm P); d - P5(130ppm P)

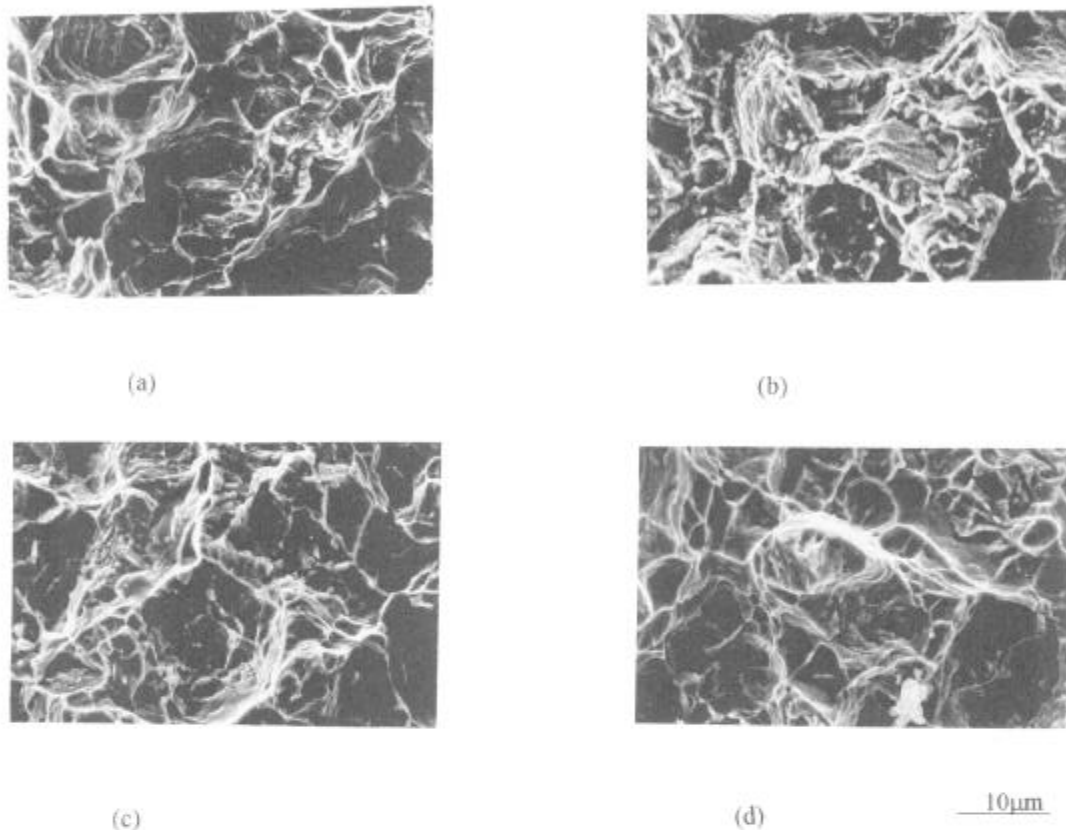


Figure 10 Fractography observation on the effect of sulfur and phosphorus in IN718.
 a - S1(15ppm S); b - S4(175ppm S); c - P2(25ppm P); d - P5(130ppm P)

among our experimental heats characterizes typical deformed and prolonged grain structure, which is in total reverse in comparison with the S effect (see Fig.9d). SEM fractography observation direct on the fracture surfaces after 650°C stress rupture tests shows that Alloy S1 with the lowest content of S(15ppm) characterizes more ductile intergranular fracture mode (see Fig.10a and b). However, phosphorus promotes the fracture to be more ductile as shown in Fig.10c and 10d.

From above mentioned comprehensive experimental results it can be concluded that the effects of P and S on mechanical properties in IN 718 are as follows:

1. Phosphorus and sulfur both have almost no influence on strengths and ductilities at room temperature tensile test.
2. Phosphorus also has no effects on the yield and ultimate strengths and elongation at 650°C tensile test. However, sulfur has an obviously decreasing effect on 650°C tensile elongation but no effect on yield and ultimate strengths.

3. Sulfur has a remarkable detrimental effect on stress rupture (creep) life and especially on ductility loss (tertiary creep) at 650°C. However, phosphorus is in total difference to sulfur effect. Phosphorus can increase stress rupture life and ductility, as well as prolong secondary creep and develop tertiary creep both.

Microstructure and fractography observation reveals that phosphorus and sulfur have only the effect on these mechanical properties characterized with intergranular fracture, especially for high temperature stress rupture or creep failures, however the effects of P and S are in totally different manner.

Special attention should be paid, that P has certain high temperature strengthening and ductility improvement effects. Only a few experimental results in the recent years show that phosphorus can be beneficial for high temperature stress rupture, creep and creep-fatigue properties in IN718⁽⁵⁾, Ni-Cr-Fe⁽⁶⁾ and 304L⁽⁷⁾ austenitic alloys as we have in this investigation. To the best of

today's knowledge, the reason of beneficial effect of P in these alloys is still not clear yet.

Phosphorus and sulfur seriously aggravate dendritic segregation during solidification and both are concentrated at grain boundaries after heat treatment of wrought IN718. These effects have been already experimentally determined^(2-5,8). Theoretical explanation is tried to make that based on the first principle interatomic potential study suggested by Wang et al.⁽⁹⁾ to calculate the doping effects on the NiΣ11[110] tilt grain boundary by using Discrete Variational X_α Method (DVM). However, their results⁽¹⁰⁾ indicate that both P and S elevate the binding energy of atom clusters at grain boundaries and the equilibrium lattice constant (ELC) at grain boundaries in nickel. The ELC of pure nickel grain boundary is 3.6000Å while the P-doping's and the S-doping's grain boundaries are 3.8555Å and 3.8823Å respectively. Therefore, the segregation of P and S at grain boundaries leads to the grain boundary embrittlement in nickel. However, Inconel 718 is a very complicated multi-component alloy system. An hypothesis is trying to take in consideration, that phosphorus may interact with the other elements and they may co-exist at the grain-boundaries to decrease grain boundary binding energy and to increase grain boundary cohesive force. In results of these, phosphorus may effectively strengthen grain boundary and to retard grain boundary crack til to failure at high temperature tests. A further research program is going to enlighten the P effect in IN718.

Conclusions

1. Phosphorus and sulfur both have almost no influence on strengths and ductilities at room temperature tensile test. Phosphorus also has no effect on the yield and ultimate strengths and elongation at 650°C tensile test. However, sulfur has an obviously decreasing effect on 650°C tensile elongation but no effect on yield and ultimate strengths.
2. Sulfur has a remarkable detrimental effect on stress rupture life and especially on ductility loss at 650°C. However, phosphorus is in total difference to sulfur effect, generally can increase stress rupture (creep) life and ductility.
3. Microstructure observation on grain structure, δ-phase and strengthening phase γ'' and γ' can not reveal the effect of P and S on the morphology and amount of precipitates. Fractography analyses show different patterns of failed stress rupture specimens with the variation of P and S contents. Experimental results lead us to consider the segregation behaviors of P and S at grain boundaries, however the effect of P and S should be different.
4. Sulfur is regarded as a detrimental impurity in Inconel 718 and it should be controlled at the lowest level in alloy production.

5. From the view point of serious segregation problem in Inconel 718 the production of low segregation Inconel 718, suggested to control P content at very low level (<10ppm), was successfully conducted. Industrial results have not shown any benefits for mechanical properties. However, laboratory experimental results show that very low level phosphorus leads stress rupture (creep) life loss.

6. Phosphorus seems to be beneficial for stress rupture life and ductility improvement, however its mechanism is still not clear yet.

References

- (1) A. Mitchell, "Progress in Understanding Clean Metal Production for IN 718", Superalloys 718, 625, 706 and Various Derivatives Ed. E.A. Loria, TMS(1994) P.109
- (2) Y. Zhu et al., "Effect of P, S, B and Si on the Solidification on INCONEL 718 Alloy", Superalloys 718, 625, 706 and Various Derivatives Ed. E.A. Loria, TMS(1994) P.89
- (3) C. Chen, R.G. Thompson and D.W. Davis, "A Study of Effects of Phosphorus, Sulfur, Boron and Carbon on Laves and Carbide Formation in Alloy 718", Superalloys 718, 625, 706 and Various Derivatives Ed. E.A. Loria, TMS(1991) P.81
- (4) Y. Zhu et al., "A New Way to Improve the Superalloys", Superalloys 1992 Eds. S.D. Antolovich et al., TMS(1992) P.145
- (5) W.D. Cao and R.L. Kennedy, "The effect of Phosphorus on Mechanical Properties of Alloy 718", Superalloys 718, 625, 706 and Various Derivatives Ed. E.A. Loria, TMS(1994)P.463
- (6) G.S. Was, J.K. Sung and T.M. Angeliu, "Effects of Grain Boundary Chemistry on the Intergranular Cracking Behaviors of Ni-16Cr-9Fe in High-Temperature Water", Met. Trans. 23A(1992) P.3343
- (7) Y.C. Yoon et al, "Effect of Phosphorus on the Creep-Fatigue Interaction in AISI 304L Stainless Steel, J. of the Korean Inst. of Met. & Mater. 30(1992) P. 1401
- (8) R.G. Thompson, Personal Communication, Univ. of Alabama at Birmingham (1995)
- (9) Wang Chongyu et al., "A First Principle Interatomic Potential and Application to Grain Boundary in Nickel", Phys. Letter A197 (1995) P.447
- (10) Wang Chongyu, Wang Ligen and Wang Fuhe, "Binding Energy and Doping Effect of Grain Boundary on the First Principle Calculations for Transition Metal", Inter. Conf. of IUMRS in Asia (1993) P.109